

# ARNE®

Cold work tool steel

COLD WORK

PLASTIC MOULDING

HOT WORK

HIGH PERFORMANCE STEEL



This information is based on our present state of knowledge and is intended to provide general notes on our products and their uses. It should not therefore be construed as a warranty of specific properties of the products described or a warranty for fitness for a particular purpose.

## General

Arne general purpose oil-hardening tool steel is a versatile manganese-chromium-tungsten steel suitable for a wide variety of cold-work applications. Its main characteristics include:

- Good machinability
- Good dimensional stability in hardening
- A good combination of high surface hardness and toughness after hardening and tempering.

These characteristics combine to give a steel suitable for the manufacture of tooling with good tool-life and production economy.

Arne can be supplied in various finishes including hot-rolled, pre-machined, fine-machined and precision ground. It is also available in the form of hollow bar.

Typical analysis %	C 0,95	Mn 1,1	Cr 0,6	W 0,6	V 0,1
Standard specification	AISI O1, W.-Nr. 1.2510				
Delivery condition	Soft annealed approx. 190 HB				
Colour code	Yellow				

## Applications

Tools for	Material thickness	HRC
<b>Cutting</b> Blanking, punching, piercing, cropping, shearing, trimming clipping	up to 3 mm (1/8") 3– 6 mm (1/8–1/4") 6–10 mm (1/4–13/32")	60–62 56–60 54–56
Short cold shears		54–60
Clipping and trimming tools for forgings	Hot Cold	58–60 56–58
<b>Forming</b> Bending, raising, drawing, rim rolling, spinning and flow forming		56–62
Small coining dies		56–60
Gauges, measuring tools Turning centres Guide bushes, ejector pins, high duty, small/medium drills and taps Small gear wheels, pistons, nozzles, cams		58–62

## Properties

### PHYSICAL DATA


Hardened and tempered to 62 HRC. Data at ambient temperature and elevated temperature.

Temperature	20°C (68°F)	200°C (375°F)	400°C (750°F)
Density kg/m <sup>3</sup> lbs/in <sup>3</sup>	7 800 0,282	7 750 0,280	7 700 0,278
Modulus of elasticity N/mm <sup>2</sup> kp/mm <sup>2</sup> tsi psi	190 000 19 500 12 500 28 x 10 <sup>6</sup>	185 000 19 000 12 200 27 x 10 <sup>6</sup>	170 000 17 500 11 200 25 x 10 <sup>6</sup>
Coefficient of thermal expansion per °C from 20°C per °F from 68°F	– –	11,7 x 10 <sup>-6</sup> 6,5 x 10 <sup>-6</sup>	11,4 x 10 <sup>-6</sup> 6,3 x 10 <sup>-6</sup>
Thermal conductivity W/m °C Btu in/ft <sup>2</sup> h °F	32 222	33 229	34 236
Specific heat J/kg °C Btu/lb. °F	460 0,11	– –	– –

### COMPRESSIVE STRENGTH

The figures are to be considered approximate.

Hardness HRC	Compressive strength	
	R <sub>m</sub> N/mm <sup>2</sup>	R <sub>c0,2</sub> N/mm <sup>2</sup>
62	3000	2200
60	2700	2150
55	2200	1800
50	1700	1350

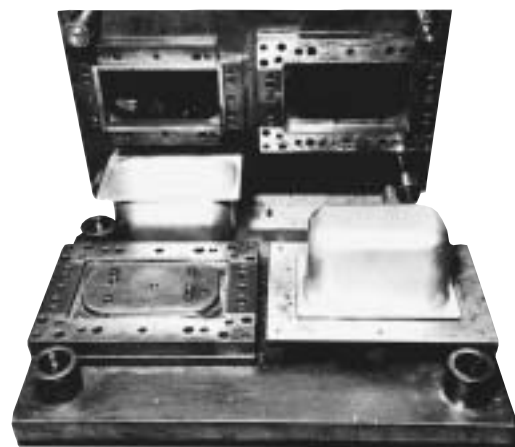

Clipping and edging tool in Arne tool steel to clip and form edge of 0,914 mm (0,036") thick stainless steel container approx. 254 x 152 x 203 mm (10" x 6" x 8").

# Heat treatment

## SOFT ANNEALING

Protect the steel and heat through to 780°C (1435°F). Then cool in the furnace at 15°C (27°F) per hour to 650°C (1200°F), then freely in air.

## STRESS-RELIEVING

After rough machining the tool should be heated through to 650°C (1200°F), holding time 2 hours. Cool slowly to 500°C (930°F) then freely in air.

## HARDENING

*Preheating temperature:* 600–700°C (1110–1290°F)

*Austenitizing temperature:* 790–850°C (1450–1560°F)

Temperature		Soaking* time minutes	Hardness before tempering
°C	°F		
800	1470	30	approx. 65 HRC
825	1520	20	approx. 65 HRC
850	1560	15	approx. 63 HRC

\*Soaking time = time at austenitizing temperature after the tool is fully heated through.


*Protect the part against decarburization and oxidation during hardening.*

## QUENCHING MEDIA

- Oil
- Martempering bath. Temperature 180–225°C (360–435°F), then cooling in air.

*Note:* Temper the tool as soon as its temperature reaches 50–70°C (120–160°F).


## Hardness as a function of hardening temperature

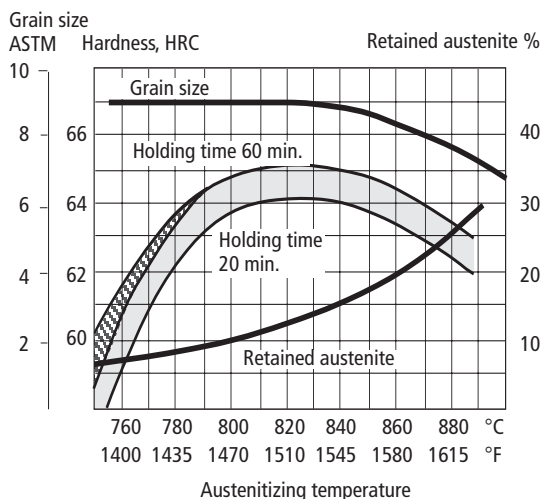

## TEMPERING

Choose the tempering temperature according to the hardness required by reference to the tempering graph. Temper twice with intermediate cooling to room temperature. Lowest tempering temperature 180°C (360°F). Holding time at temperature minimum 2 hours.

## Tempering graph

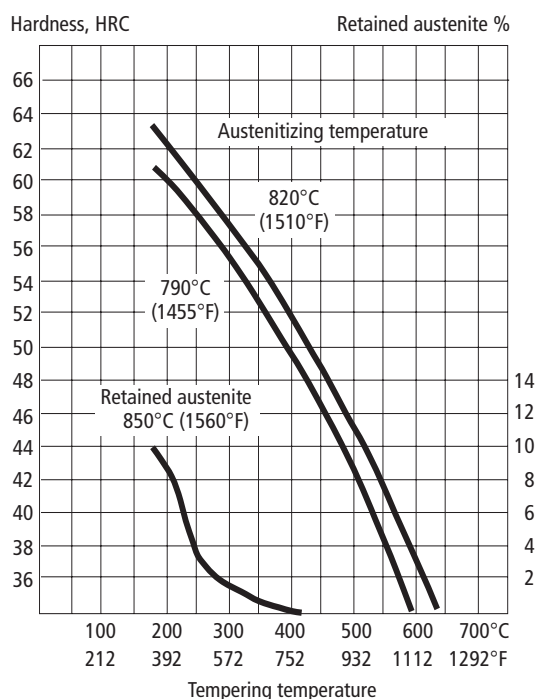

## MARTEMPERING

Tools at austenitizing temperature are immersed in the martempering bath for the time indicated, then cooled in air to not lower than 100°C (210°F). Temper immediately as with oil-quenching.

Austenitizing temperature		Temp. of martemp. bath,		Holding time in martemp. bath minutes	Surface hardness prior to tempering (obtained by martempering)
°C	°F	°C	°F		
825	1520	225	435	max. 5	64 ± 2 HRC
825	1520	200	390	max. 10	63 ± 2 HRC
825	1520	180	355	max. 20	62 ± 2 HRC
850	1560	225	435	max. 10	62 ± 2 HRC

**DIMENSIONAL CHANGES DURING HARDENING**


Sample plate, 100 x 100 x 25 mm, 4" x 4" x 1"

		Width %	Length %	Thickness %
Oil hardening from 830°C (1530°F)	min.	+0,03	+0,04	–
	max.	+0,10	+0,10	+0,02
Martempering from 830°C (1530°F)	min.	+0,04	+0,06	–
	max.	+0,12	+0,12	+0,02

**DIMENSIONAL CHANGES DURING TEMPERING**

Plancha de muestra, 100 x 100 x 25 mm

Dimensional change %

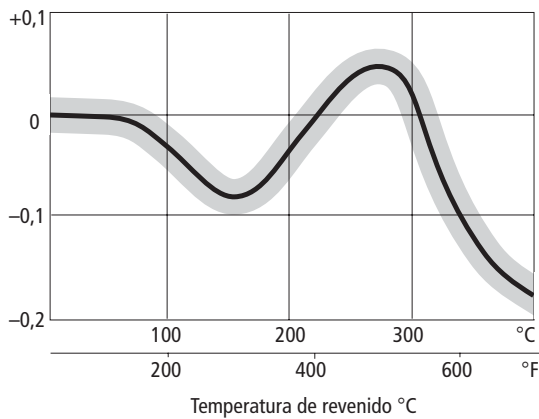

*Note:* The dimensional changes on hardening and tempering should be added together. Recommended allowance 0,25 %.

**SUB-ZERO TREATMENT AND AGING**


Pieces requiring maximum dimensional stability should be sub-zero treated and/or artificially aged, as volume changes may occur in the course of time. This applies, for example, to measuring tools like gauges and certain structural components.

**Sub-zero treatment**

Immediately after quenching the piece should be sub-zero treated to between  $-70$  and  $-80^{\circ}\text{C}$  ( $-95$  to  $-110^{\circ}\text{F}$ ), soaking time 3–4 hours, followed by tempering or aging. Sub-zero treatment will give a hardness increase of 1–3 HRC. Avoid intricate shapes as there will be risk of cracking.

**Aging**

Tempering after quenching is replaced by aging at  $110$ – $140^{\circ}\text{C}$  ( $230$ – $285^{\circ}\text{F}$ ). Holding time 25–100 hours.

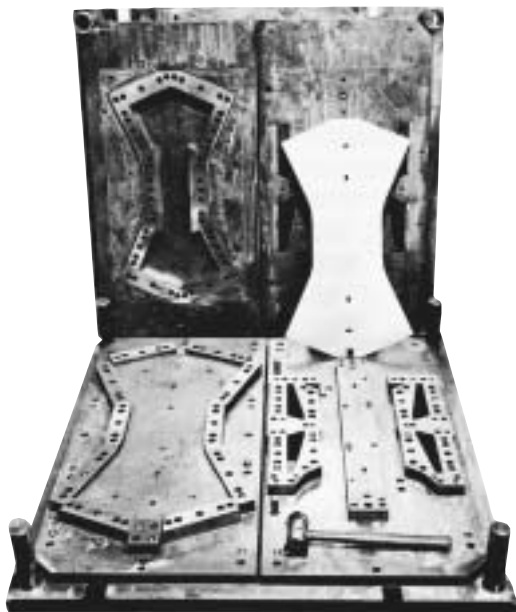

*Blanking tool made from fine-machined Arne tool steel.*

# Machining recommendations

The following tables give machining data for Arne in soft annealed condition. Hardness 190 HB. The data are to be considered as guiding values, which must be adapted to existing local conditions.

## TURNING

Cutting data parameters	Turning with carbide		Turning with high speed steel Fine turning
	Rough turning	Fine turning	
Cutting speed ( $v_c$ ) m/min f.p.m.	160–210 525–690	210–260 690–850	20–25 65–80
Feed (f) mm/r i.p.r.	0,2–0,4 0,008–0,016	0,05–0,2 0,002–0,008	0,05–0,3 0,002–0,01
Depth of cut ( $a_p$ ) mm inch	2–4 0,08–0,2	0,5–2 0,02–0,08	0,5–3 0,02–0,10
Carbide designation ISO	P20–P30 Coated carbide	P10 Coated carbide or cermet	—

## MILLING

### Face and square shoulder milling

Cutting data parameters	Milling with carbide	
	Rough milling	Fine milling
Cutting speed ( $v_c$ ) m/min f.p.m.	170–250 560–820	250–290 820–950
Feed ( $f_z$ ) mm/tooth inch/tooth	0,2–0,4 0,008–0,016	0,10–0,2 0,004–0,008
Depth of cut ( $a_p$ ) mm inch	2–5 0,08–0,2	–2 –0,08
Carbide designation ISO	P20–P40 Coated carbide	P10–P20 Coated carbide or cermet

### End milling

Cutting data parameters	Type of milling		
	Solid carbide	Carbide indexable insert	High speed steel
Cutting speed ( $v_c$ ) m/min f.p.m.	150–190 490–620	160–220 525–720	25–30 <sup>1)</sup> 80–100 <sup>1)</sup>
Feed ( $f_z$ ) mm/tooth inch/tooth	0,03–0,2 <sup>2)</sup> 0,0012–0,008 <sup>2)</sup>	0,08–0,2 <sup>2)</sup> 0,003–0,008 <sup>2)</sup>	0,05–0,35 <sup>2)</sup> 0,002–0,014 <sup>2)</sup>
Carbide designation ISO	K20, P40	P20–P30	—

<sup>1)</sup> For coated end mills  $v_c = 45–50$  m/min. (150–160 f.p.m.)

<sup>2)</sup> Depending on radial depth of cut and cutter diameter.

## DRILLING

### High speed steel twist drill

Drill diameter		Cutting speed ( $v_c$ )		Feed (f)	
mm	inch	m/min	f.p.m.	mm/r	i.p.r.
– 5	–3/16	15–17*	49–56*	0,08–0,20	0,003–0,008
5–10	3/16–3/8	15–17*	49–56*	0,20–0,30	0,008–0,012
10–15	3/8–5/8	15–17*	49–56*	0,30–0,35	0,012–0,014
15–20	5/8–3/4	15–17*	49–56*	0,35–0,40	0,014–0,016

\* For coated HSS drills  $v_c = 26–28$  m/min. (85–90 f.p.m.)

### Carbide drill

Cutting data parameters	Type of drill		
	Indexable insert	Solid carbide	Taladro con Brazed carbide <sup>1)</sup>
Cutting speed ( $v_c$ ) m/min f.p.m.	200–220 655–720	110–140 360–460	70–90 230–295
Feed (f) mm/r i.p.r.	0,05–0,25 <sup>2)</sup> 0,002–0,01 <sup>2)</sup>	0,10–0,25 <sup>2)</sup> 0,004–0,01 <sup>2)</sup>	0,15–0,25 <sup>2)</sup> 0,006–0,01 <sup>2)</sup>

<sup>1)</sup> Drills with internal cooling channels and brazed carbide tip

<sup>2)</sup> Depending on drill diameter

## GRINDING

General grinding wheel recommendation for Arne is given below. More information can be found in the Uddeholm publication "Grinding of Tool Steel".

Type of grinding	Wheel recommendation	
	Soft annealed condition	Hardened condition
Face grinding straight wheel	A 46 HV	A 46 HV
Face grinding segments	A 24 GV	A 36 GV
Cylindrical grinding	A 46 LV	A 60 KV
Internal grinding	A 46 JV	A 60 IV
Profile grinding	A 100 LV	A 120 JV

## Welding

Good results when welding tool steel can be achieved if proper precautions are taken during welding (elevated working temperature, joint preparation, choice of consumables and welding procedure). If the tool is to be polished or photo-etched, it is necessary to work with an electrode type of matching composition.

Welding method	Working temperature	Consumables	Hardness after welding
MMA (SMAW)	200–250°C	AWS E312 84.52 UTP 67S Castolin 2 Castolin N 102	300 HB ESAB OK 53–54 HRC 55–58 HRC 54–60 HRC 54–60 HRC
TIG	200–250°C	AWS ER312 UTPA 67S UTPA 73G2 Castotig 5	300 HB 55–58 HRC 53–56 HRC 60–64 HRC

## Electrical-discharge machining

If spark-erosion, EDM, is performed in the hardened and tempered condition, the tool should then be given an additional temper at approx. 25°C (50°F) below the previous tempering temperature.

## Further information

Please contact your local Uddeholm office for further information on the selection, heat treatment, application and availability of Uddeholm tool steels.

## Relative comparison of Uddeholm cold work tool steel

### MATERIAL PROPERTIES AND RESISTANCE TO FAILURE MECHANISMS

Uddeholm grade	Hardness/ Resistance to plastic deformation	Machinability	Grindability	Dimension stability	Resistance to		Fatigue cracking resistance	
					Abrasive wear	Adhesive wear	Ductility/ resistance to chipping	Toughness/ gross cracking
ARNE	████	████████	████████	█	████	████	████	████
CALMAX	████	████████	████████	████████	████	████	████████	████████
CALDIE	████████	████████	████████	████████	████	████████	████████	████████
RIGOR	████	████████	████	████	████	████	████	████
SLEIPNER	████████	████████	████	████	████	████	████	████
SVERKER 21	████	████	██	████	████	█	██	████
SVERKER 3	████	██	█	████	████████	█	██	██
VANADIS 4 Extra	████████	████████	████	████████	████	████	████	████
VANADIS 6	████	██	██	████	████	████	████	██
VANADIS 10	████	██	█	████	████	████	██	██
VANADIS 23	████	████	████	████	████	████	████	██

## UDDEHOLM EUROPE

### AUSTRIA

UDDEHOLM  
Hansaallee 321  
D-40549 Düsseldorf  
Telephone: +49 211 535 10  
Telefax: +49 211 535 12 80

### BELGIUM

UDDEHOLM N.V.  
Waterstraat 4  
B-9160 Lokeren  
Telephone: +32 9 349 11 00  
Telefax: +32 9 349 11 11

### CROATIA

BOHLER UDDEHOLM Zagreb  
d.o.o. za trgovinu  
Zitnjak b.b  
10000 Zagreb  
Telephone: +385 1 2459 301  
Telefax: +385 1 2406 790

### CZECHIA

BOHLER UDDEHOLM CZ s.r.o.  
Division Uddeholm  
U silnice 949  
161 00 Praha 6 Ruzyně  
Czech Republic  
Telephone: +420 233 029 850,8  
Telefax: +420 233 029 859

### DENMARK

UDDEHOLM A/S  
Kokmose 8, Bramdrupdam  
DK-6000 Kolding  
Telephone: +45 75 51 70 66  
Telefax: +45 75 51 70 44

### ESTONIA

UDDEHOLM TOOLING AB  
Silikatsiidid 7  
EE-0012 Tallinn  
Telephone: +372 655 9180  
Telefax: +372 655 9181

### FINLAND

OY UDDEHOLM AB  
Ritakuja 1, PL 57,  
FIN-01741 VANTAA  
Telephone: +358 9 290 490  
Telefax: +358 9 2904 9249

### FRANCE

UDDEHOLM S.A.  
12 Rue Mercier, Z.I. de Mitry-Compans  
F-77297 Mitry Mory Cedex  
Telephone: +33 (0)1 60 93 80 10  
Telefax: +33 (0)1 60 93 80 01

#### Branch office

UDDEHOLM S.A.  
77bis, rue de Vesoul  
La Nef aux Métiers  
F-25000 Besançon  
Telephone: +33 381 53 12 19  
Telefax: +33 381 53 13 20

### GERMANY

UDDEHOLM  
Hansaallee 321  
D-40549 Düsseldorf  
Telephone: +49 211 535 10  
Telefax: +49 211 535 12 80

#### Branch offices

UDDEHOLM  
Falkenstrasse 21  
D-65812 Bad Soden/TS.  
Telephone: +49 6196 659 60  
Telefax: +49 6196 659 625

### UDDEHOLM

Albstraße 10  
D-73765 Neuhausen  
Telephone: +49 715 898 65-0  
Telefax: +49 715 898 65-25

### GREAT BRITAIN, IRELAND

UDDEHOLM UK LIMITED  
European Business Park  
Taylors Lane, Oldbury  
West Midlands B69 2BN  
Telephone: +44 121 552 55 11  
Telefax: +44 121 544 29 11  
Dublin Telephone: +353 1 45 14 01

### GREECE

UDDEHOLM STEEL TRADING  
COMPANY  
20, Athinon Street  
G-Piraeus 18540  
Telephone: +30 2 10 41 72 109/41 29 820  
Telefax: +30 2 10 41 72 767

### SKLERO S.A.

Steel Trading Comp. and  
Hardening Shop  
Frixou 11/Nikif. Ouranou  
G-54627 Thessaloniki  
Telephone: +30 31 51 46 77  
Telefax: +30 31 54 12 50

### HUNGARY

UDDEHOLM TOOLING/BOK  
Dunaharaszti, Jedlik Anyos út 25  
H-2331 Dunaharaszti 1.Pf. 110  
Telephone/Telefax: +36 24 492 690

### ITALY

UDDEHOLM Italia S.p.A.  
Via Palizzi, 90  
I-20157 Milano  
Telephone: +39 02 35 79 41  
Telefax: +39 02 390 024 82

### LATVIA

UDDEHOLM TOOLING AB  
Deglava street 50  
LV-1035 Riga  
Telephone: +371 7 701 983, -981, -982  
Telefax: +371 7 701 984

### LITHUANIA

UDDEHOLM TOOLING AB  
BE PLIENAS IR METALAI  
T. Masiulio 18b  
LT-3014 Kaunas  
Telephone: +370 37 370613, -669  
Telefax: +370 37 370300

### THE NETHERLANDS

UDDEHOLM B.V.  
Isolatorweg 30  
NL-1014 AS Amsterdam  
Telephone: +31 20 581 71 11  
Telefax: +31 20 684 86 13

### NORWAY

UDDEHOLM A/S  
Jernkroken 18  
Postboks 85, Kalbakken  
N-0902 Oslo  
Telephone: +47 22 91 80 00  
Telefax: +47 22 91 80 01

### POLAND

INTER STAL CENTRUM  
Sp. z. o.o./Co. Ltd.  
ul. Kolejowa 291, Dziekanów Polski  
PL-05-092 Lomianki  
Telephone: +48 22 429 2260  
Telefax: +48 22 429 2266

### PORTUGAL

F RAMADA Aços e Industrias S.A.  
P.O. Box 10  
P-3881 Ovar Codex  
Telephone: +351 56 58 61 11  
Telefax: +351 56 58 60 24

### ROMANIA

BÖHLER Romania SRL  
Uddeholm Branch  
Str. Atomistilor Nr 14A  
077125 Magurele Jud Ilfov  
Telephone: +40 214 575007  
Telefax: +40 214 574212

### RUSSIA

UDDEHOLM TOOLING CIS  
25 A Bolshoy pr PS  
197198 St. Petersburg  
Telephone: +7 812 233 9683  
Telefax: +7 812 232 4679

### SLOVAKIA

UDDEHOLM Slovakia  
Nástrojové ocele, s.r.o.  
KRÁCINY 2  
036 01 Martin  
Telephone: +421 842 4 300 823  
Telefax: +421 842 4 224 028

### SLOVENIA

UDDEHOLM Italia S.p.A.  
Via Palizzi, 90  
I-20157 Milano  
Telephone: +39 02 35 79 41  
Telefax: +39 02 390 024 82

### SPAIN

UDDEHOLM  
Guifré 690-692  
E-08918 Badalona, Barcelona  
Telephone: +34 93 460 1227  
Telefax: +34 93 460 0558

#### Branch office

UDDEHOLM  
Barrio San Martin de Arteaga, 132  
Pol.Ind. Torrelarragoiti  
E-48170 Zamudio  
(Bizkaia)  
Telephone: +34 94 452 13 03  
Telefax: +34 94 452 13 58

### SWEDEN

UDDEHOLM TOOLING  
SVENSKA AB  
Aminogatan 25  
SE-431 53 Mölndal  
Telephone: +46 31 67 98 50  
Telefax: +46 31 27 02 94

### SWITZERLAND

HERTSCH & CIE AG  
General Wille Strasse 19  
CH-8027 Zürich  
Telephone: +41 1 208 16 66  
Telefax: +41 1 201 46 15

## UDDEHOLM NORTH AMERICA

### USA

UDDEHOLM  
4902 Tollview Drive  
Rolling Meadows IL 60008  
Telephone: +1 847 577 22 20  
Telefax: +1 847 577 80 28

### UDDEHOLM

548 Clayton Ct.,  
Wood Dale IL 60191  
Telephone: +1 630 350 10 00  
Telefax: +1 630 350 08 80

### UDDEHOLM

9331 Santa Fe Springs Road  
Santa Fe Springs, CA 90670  
Telephone: +1 562 946 65 03  
Telefax: +1 562 946 77 21

### UDDEHOLM

220 Cherry Street  
Shrewsbury, MA 01545  
Telephone: +1 508 845 1066  
Telefax: +1 508 845 3471

### CANADA

UDDEHOLM LIMITED  
2595 Meadowvale Blvd.  
Mississauga, Ontario L5N 7Y3  
Telephone: +1 905 812 9440  
Telefax: +1 905 812 8659

### MEXICO

ACEROS BOHLER UDDEHOLM,  
S.A. de C.V.  
Calle 8 No 2, Letra "C"  
Fraccionamiento Industrial Alce Blanco  
C.P. 52787 Naucalpan de Juarez  
Estado de Mexico  
Telephone: +52 55 9172 0242  
Telefax: +52 55 5576 6837

### UDDEHOLM

Lerdo de Tejada No.542  
Colonia Las Villas  
66420 San Nicolas de Los Garza, N.L.  
Telephone: +52 8-352 5239  
Telefax: +52 8-352 5356

## UDDEHOLM SOUTH AMERICA

### ARGENTINA

UDDEHOLM S.A  
Mozart 40  
1619-Centro Industrial Garin  
Garin-Prov. Buenos Aires  
Telephone: +54 332 744 4440  
Telefax: +54 332 745 3222

### BRAZIL

UDDEHOLM ACOS ESPECIAIS Ltda.  
Estrada Yae Massumoto, 353  
CEP 09842-160  
Sao Bernardo do Campo - SP Brazil  
Telephone: +55 11 4393 4560, -4554  
Telefax: +55 11 4393 4561

## UDDEHOLM SOUTH AFRICA

UDDEHOLM Africa (Pty) Ltd.  
P.O. Box 539  
ZA-1600 Isando/Johannesburg  
Telephone: +27 11-974 2781  
Telefax: +27 11-392 2486

## UDDEHOLM AUSTRALIA

BOHLER-UDDEHOLM Australia  
129-135 McCredie Road  
Guildford NSW 2161  
Private Bag 14  
Telephone: +61 2 9681 3100  
Telefax: +61 2 9632 6161

#### Branch offices

Sydney, Melbourne, Adelaide,  
Brisbane, Perth, Newcastle,  
Launceston, Albury, Townsville

## ASSAB

### ASSAB INTERNATIONAL

Skytteholmsvägen 2  
P O Box 42  
SE-171 11 Solna  
Sweden  
Telephone: +46 8 564 616 70  
Telefax: +46 8 25 02 37

#### Subsidiaries

India, Iran, Turkey, United Arab  
Emirates

#### Distributors in

Africa, Latin America, Middle East

### ASSAB PACIFIC

ASSAB Pacific Pte. Ltd  
171, Chin Swee Road  
No. 07-02, San Centre  
Singapore 169877  
Telephone: +65 534 56 00  
Telefax: +65 534 06 55

#### Subsidiaries

China, Hong Kong, Indonesia, Japan,  
Korea, Malaysia, Philippine Islands,  
Singapore, Taiwan, Thailand

When the first idea pops into your head, throughout the development process to the release of the new product, we'll be your partner. As the world's leading supplier of tooling materials and related services, we can be trusted. Meet us under the Uddeholm and ASSAB brands, wherever in the world you have your business.

